



تشدید پلاسمونی وابسته به شدت نور ورودی در لایه گرافن

مهدی صادقی ، وحید احمدی

دانشکده مهندسی برق و کامپیوتر، دانشگاه تربیت مدرس ، تهران

چکیده- در این مقاله ما به مطالعه تحریک پلاسمون پلاریتون های سطحی در حضور میدان های الکتریکی بالا بر روی سطح تک لایه گرافن با استفاده از پیکربندی کرشمان-رادر می پردازیم. ما پاشندگی را برای گرافن با کیفیت بالا در نظر می گیریم به طوریکه در این حالت میزان انرژی پلاسمون پلاریتون ها بسیار بزرگتر از انرژی تلفاتی است. نتایج نشان می دهند که برای موج های الکترومغناطیسی با شدت بالا، ثابت انتشار پلاسمون پلاریتون های سطحی رابطه غیرخطی با زاویه تابش موج الکترومغناطیسی ورودی دارد. همچنین در شدت های بالا، پاشندگی پلاسمون پلاریتون های سطحی دارای تکینگی در بعضی فرکانس ها هستند که منجر به تشدیدهای پلاسمونی بیشتر می شود. از این پدیده می توان برای طراحی فیلترهای زاویه و فرکانسی استفاده کرد که قابل تنظیم با شدت نور ورودی است.

کلید واژه- گرافن ، پلاسمونیک ، کرشمان-رادر ، پاشندگی.

Intensity-dependent plasmonic resonance of graphene layer

Mehdi Sadeghi ^{1,a)}, Vahid Ahmadi ^{1,b)}

¹⁾ Department of Electrical & Computer Engineering, University of Tarbiat Modares, Tehran, 14115-111, Iran.

a) sadeghi.m@modares.ac.ir b) Corresponding author: v_ahmadi@modares.ac.ir

Abstract- In this paper, we study excitation of surface plasmon polaritons (SPPs) by Kretschmann-Raether configuration for graphene layer sandwiched between two dielectrics for enough high intensity input electromagnetic (EM) wave. We consider the dispersion of SPPs for high quality graphene layer in which scattering loss is much lower than SPPs energy. Results show that for rather high intensity EM wave, propagation constants of SPPs show nonlinear dependence to incidence angle. Also dispersion curves of surface plasmon polaritons have singularity at some frequencies which results to more plasmonic resonances. These phenomena can be used to design angle and frequency filters which are tunable by intensity of control pump.

Keywords: Graphene, Plasmonics, Kretschmann-Raether, Dispersion

1. Introduction

Graphene has shown astonishing electrical, optical and photonic properties [1]. Among them, we can mention electro-statistic tunability of charge carriers, low energy loss at terahertz frequencies, high confinement of SPPs traveling on its surface due to its 2 dimensional nature [2]. Based on above features, many structures like plasmonic filters [3], modulators [4], sensors [5] have been proposed. Significant light-matter interaction in graphene leads to very large optical susceptibilities in comparison to noble metals and conventional dielectrics [6] which motivated many researchers to utilize it in applications such as switches [7], bistable devices [8] and third harmonic generation [9]. Here, we study plasmonic resonance of graphene in Kretschmann-Raether configuration excited by high intensity input. Numerical simulation results show that at enough large intensities a second plasmonic resonance arises which can be adjusted by intensity of input optical wave. This characteristic can be used in intensity-tunable filters.

2. Materials and methods

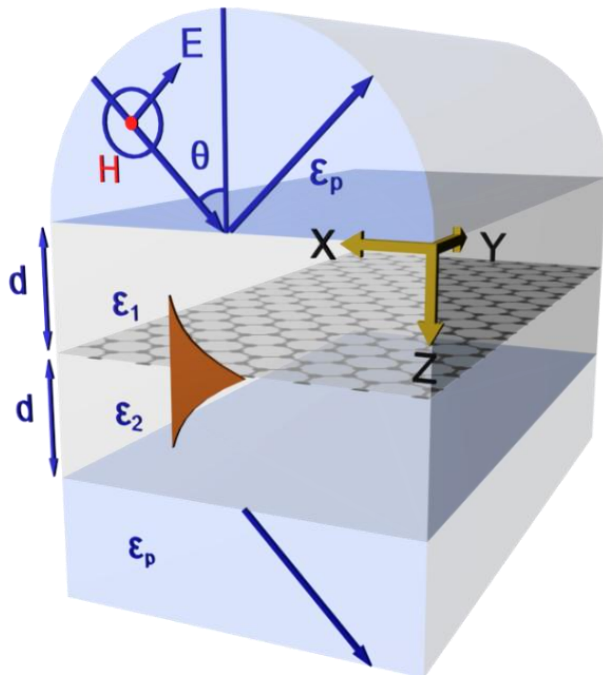


Fig. 1: Configuration of Kretschmann-Raether structure [8].

Our proposed configuration is depicted in Fig.1. A graphene sheet is sandwiched between two dielectrics with dielectric constants of ϵ_1 and ϵ_2 with thickness of d and lies parallel to XY surface.

The incident TM light propagates in the Z direction with the angle of θ respect to normal of graphene surface. The Kretschmann-Raether configuration is used to excite SPPs. Therefore a prism with dielectric constant of $\epsilon_p > \epsilon_1 > \epsilon_2$ is used to satisfy conservation of momentum law. Prism is made of Ge with dielectric constant of 16. Inner dielectrics are CaF₂ with dielectric constants of 1.69. The CaF₂ slab thickness (d) is chosen to be 30 μm . Graphene Fermi level is set to typical value of 0.23 eV. Using Maxwell equations and boundary conditions, we can write dispersion relation for TM mode as [10]

$$\frac{\epsilon_1}{\sqrt{k_{spp}^2 - \frac{\epsilon_1 \omega^2}{c^2}}} + \frac{\epsilon_2}{\sqrt{k_{spp}^2 - \frac{\epsilon_2 \omega^2}{c^2}}} = -\frac{\sigma i}{\omega \epsilon_0} \quad (1)$$

where k_{spp} the wavenumber of SPPs is, ω is the angular frequency of incident light, σ is the conductivity of graphene, ϵ_0 and c are the permittivity and speed of light in vacuum, respectively. By using Taylor expansion of graphene conductivity and for moderate high electric field, the graphene conductivity can be expressed as $\sigma = \sigma_1 + \sigma_3 |\mathbf{E}|^2$ where $\sigma_{(1)}$ and $\sigma_{(3)}$ are linear and third order surface conductivities of graphene and \mathbf{E} is the electric field on graphene surface. Second order conductivity is zero due to centro-symmetric physical structure of graphene. For high quality graphene, the inequality of $\omega \tau \gg 1$ is satisfied, so the conductivities can be expressed as [8,11]

$$\sigma_{\text{intra}}^{(1)} = \frac{iq^2}{\pi \hbar^2} \frac{E_F}{\omega} \quad (2)$$

$$\sigma_{\text{intra}}^{(3)} = -i \frac{9}{8} \frac{q^2}{\pi \hbar^2} \frac{(q v_F)^2}{\omega^3 E_F}. \quad (3)$$

where E_F is the Fermi level of graphene, ω is the angular frequency of input wave, v_F is the Fermi velocity of graphene electrons. The q and \hbar are electrical charge of electron and reduced Planks constant, respectively. Substituting Eq. (2) and Eq. (3) into Eq. (1), we can achieve dispersion relation for SPPs on graphene surface which relates SPPs wavenumber to electric field strength. Propagation constant (K_{spp}) of SPPs against different angles for electric field intensities of 1 W/cm², 4.8 W/cm² and 8.5 W/cm² are depicted in Fig. (2). At intensity of 1 W/cm², plasmonic resonance occurs at incident angle of about 32 degree. However, results show that at appropriate large intensities, there are other resonances at higher incidence angles. For input intensities of 4.8 and 8.5 W/cm², second resonance emerges at illumination angle of 80 and 63 degrees.

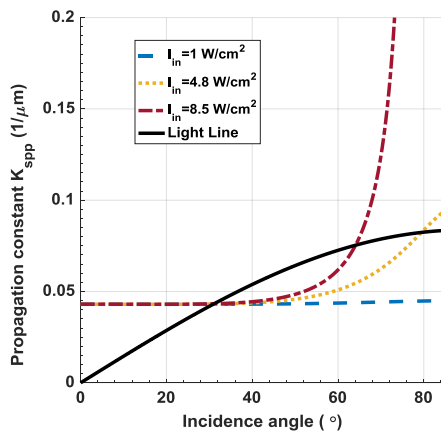


Fig. 2: Propagation constant versus input incidence angle for three different input intensities.

Transmittance versus incidence angle is shown in Fig. (3).

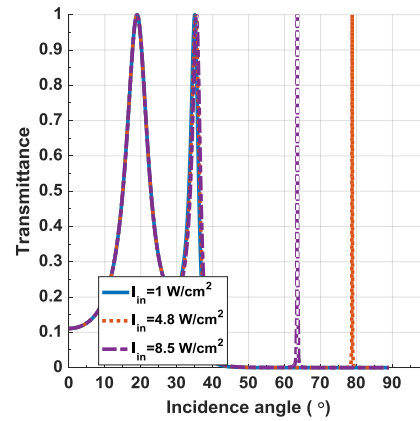


Fig. 3: Transmittance versus incidence angle.

First peak is related to Brewster angle. Second peak is the first plasmonic resonance for all intensities. Third and fourth peaks are high-intensity resonance peaks related to intensities of 8.5 W/cm² and 4.8 W/cm², respectively, which possess small full width half maximum (FWHM). This characteristic is very useful for precise intensity dependent angle filters.

Dispersion curves for three intensities of 1.9 KW/cm², 0.85 KW/cm² and 1 W/cm² are illustrated in Fig.4

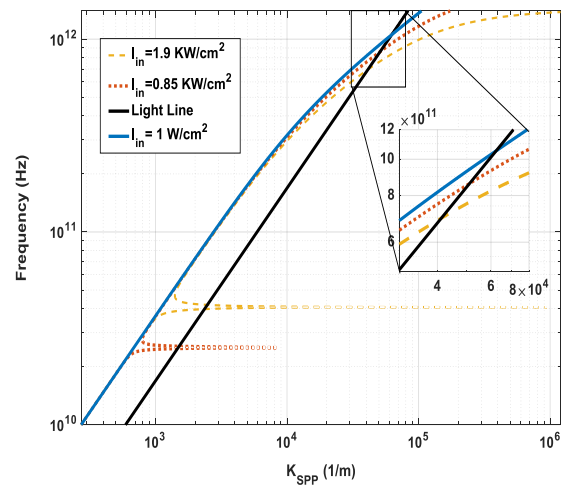


Fig. 4: Dispersion curves for three different input intensities.

It is evident that for input intensity of 1W/cm², the light line only crosses dispersion curve at a frequency of 1 THz, but at enough large intensities resonance frequency decreases slightly and also another plasmonic resonance becomes feasible.

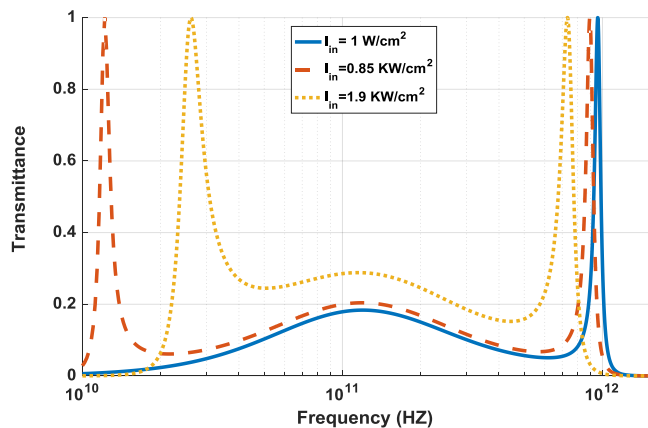


Fig. 5: Transmittance versus input light frequency.

The lower resonant frequency lies in GHz regime. For example, for input intensities of 0.85 KW/cm^2 and 1.9 KW/cm^2 , resonant frequencies of 15 GHz and 28 GHz emerges respectively which is evident in Fig. (5). To explain this resonances, we investigate conductivity behaviour against variations of frequency for various input intensities. For intensities of 0.85 KW/cm^2 and 1.9 KW/cm^2 , imaginary part of conductivity becomes zero at specific frequencies near resonant frequencies as shown in Fig. (6). At these frequencies, SPPs propagation constants become infinity. So there is a frequency at which light line crosses dispersion curve that is called resonant frequency. This resonant frequency lies in GHz range and can be shifted by input intensity. This phenomenon can be used to design tunable frequency filters by intensity in GHz regime.

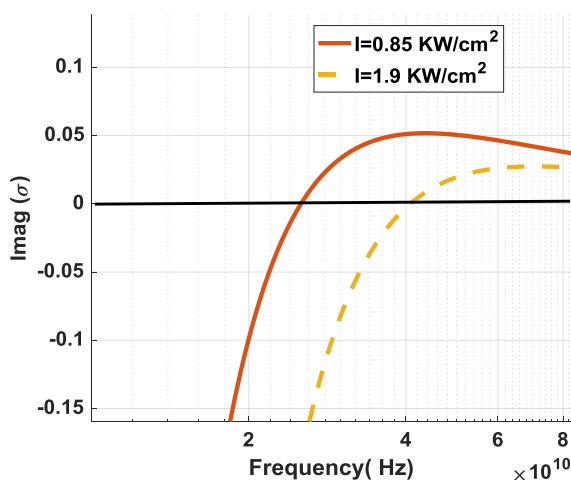


Fig. 6: Imaginary part of conductivity versus frequency.

3. Conclusions

In conclusion, we have extracted propagation constants of SPPs versus incident angle and dispersion curves related to SPPs for enough high intensities of input light excited by Kretschmann-Raether configuration. Results show that adjustable angle and frequency filters can be designed in which the controlling process can be done by means of intensity of incident wave.

References

- [1] A. K. Geim and K. S. Novoselov, "The rise of graphene," *Nat. Mater.*, vol. 6, pp. 183–191, 2007.
- [2] A. Kar, N. Goswami, and A. Saha, "Long-range surface plasmon-induced tunable ultralow threshold optical bistability using graphene sheets at terahertz frequency," *Appl. Opt.*, vol. 56, pp. 2321–2329, 2017.
- [3] H.-J. Li, L.-L. Wang, J.-Q. Liu, Z.-R. Huang, B. Sun, and X. Zhai, "Investigation of the graphene based planar plasmonic filters," *Appl. Phys. Lett.*, vol. 103, pp. 211104, 2013.
- [4] B. Sensale-Rodriguez, R. Yan, M. Zhu, D. Jena, L. Liu, and H. Grace Xing, "Efficient terahertz electro-absorption modulation employing graphene plasmonic structures," *Appl. Phys. Lett.*, vol. 101, pp. 261115, 2012.
- [5] Y. Wu, B. Yao, A. Zhang, Y. Rao, Z. Wang, Y. Cheng, Y. Gong, W. Zhang, Y. Chen, and K. S. Chiang, "Graphene-coated microfiber Bragg grating for high-sensitivity gas sensing," *Opt. Lett.*, vol. 39, pp. 1235–1237, 2014.
- [6] E. Hendry, P. J. Hale, J. Moger, A. K. Savchenko, and S. A. Mikhailov, "Coherent nonlinear optical response of graphene," *Phys. Rev. Lett.*, vol. 105, pp. 97401, 2010.
- [7] M. Sanderson, Y. S. Ang, S. Gong, T. Zhao, M. Hu, R. Zhong, X. Chen, P. Zhang, C. Zhang, and S. Liu, "Optical bistability induced by nonlinear surface plasmon polaritons in graphene in terahertz regime," *Appl. Phys. Lett.*, vol. 107, pp. 203113, 2015.
- [8] X. Dai, L. Jiang, and Y. Xiang, "Low threshold optical bistability at terahertz frequencies with graphene surface plasmons," *Sci. Rep.*, vol. 5, pp. 12271, 2015.
- [9] J. L. Cheng, N. Vermeulen, and J. E. Sipe, "Third order optical nonlinearity of graphene," *New J. Phys.*, vol. 16, pp. 53014, 2014.
- [10] M. Jablan, H. Buljan, and M. Soljačić, "Plasmonics in graphene at infrared frequencies," *Phys. Rev. B*, vol. 80, pp. 245435, 2009.
- [11] J. Guo, L. Jiang, Y. Jia, X. Dai, Y. Xiang, and D. Fan, "Low threshold optical bistability in one-dimensional gratings based on graphene plasmonics," *Opt. Express*, vol. 25, pp. 5972–5981, 2017.