The ۲۸th Iranian Conference on Optics and Photonics (ICOP ۲۰۲۲), and the ۱٤th Iranian Conference on Photonics Engineering and Technology (ICPET ۲۰۲۲).
Shahid Chamran University of Ahvaz, Khuzestan, Iran, Feb. ۱-۳, ۲۰۲۲

سنتز نانوذرات TiO_2 با روش سل-ژل برای ساخت سلول‌های خورشیدی حساس شده با رنگدانه طبیعی میوه جمبو

ماندانا شادکام[۱]، تهمینه جلالی[۱]، محسن محرابی[۱] و شهریار عصفوری[۲]

[۱]گروه فیزیک دانشگاه خلیج فارس، بوشهر، ایران؛ [۲]گروه مهندسی شیمی دانشگاه خلیج فارس، بوشهر، ایران

چکیده- در این مطالعه، نانوذرات TiO_2 به منظور دستیابی به بلورینگی بالا و اندازه کوچک ذرات، به روش سل-ژل سنتز شده و سپس مشخصه‌های نانوذره‌های تهیه شده به وسیله‌ی پراش پرتو ایکس (XRD) و طیف سنج مادون قرمز (FT-IR) ارزیابی شدند. سلول خورشیدی رنگدانه‌ای با استفاده از لایه نشانی خمیر نانوذرات TiO_2 بر روی زیرلایه شیشه‌ای FTO (اکسید قلع آلاییده شده با فلوئور) تحت عنوان فیلم اکسید نیمه رسانا ساخته شد. همچنین در این تحقیق، برای کاهش هزینه‌ها، از رنگدانه طبیعی استخراج شده از میوه جمبو استفاده شده است. پارامترهای فتوولتائیک تحت نور خورشید شبیه سازی شده با شدت تابش ۱۰۰ mW/cm^2 و تابش استاندارد (AM۱،٥) اندازه گیری شد. نتایج نشان داد بازده تبدیل انرژی ۱،۳۶٪ و سایر مشخصه های فتوولتایک شامل جریان مدار کوتاه، ولتاژ مدار باز و فاکتور پر شدن به ترتیب ٥،۸۸ mA/cm^2 ، ۰،۶۲۳٥ V و۰،۳۷۰۶ می‌باشند.

کلید واژه- رنگدانه طبیعی، روش سل-ژل، سلول‌های خورشیدی رنگدانه‌ای، فتوآند، نانوذرات TiO_2

Synthesis of TiO_2 nanoparticles using the sol-gel method to fabricate dye-sensitized solar cells with natural Syzygium Cumini fruit dye

M. Shadkam[۱], T. Jalali[۱*], M. Mehrabi[۱], and S. Osfouri [۲]

[۱]Department of Physics, Persian Gulf University, Bushehr, Iran; [۲]Department of Chemical Engineering, Persian Gulf University, Bushehr, Iran, *jalali@pgu.ac.ir

Abstract In this study, TiO_2 nanoparticles were synthesized using the sol-gel method to obtain a highly crystalline and small particle size of TiO_2; the produced nanoparticles were characterized by X-ray diffraction (XRD) and Fourier transform infrared spectroscopy (FT-IR). Dye-sensitized solar cell (DSSC) was fabricated with a layer of TiO_2 nanoparticles paste deposited on FTO (fluorine-doped tin oxide) glass substrate as a semiconductor oxide film. Also in this study, extracted natural dye from Syzygium Cumini fruit was used for decrease the cost. The photovoltaic parameters were measured using the solar simulator under an incident light intensity of ۱۰۰ mW/cm^2 and air mass (AM۱،٥). The results show power conversion efficiency (η) of ۱،۳٦٪ and other photovoltaic parameters include short circuit current density (J_{SC}), open-circuit voltage (V_{OC}) and fill factor (FF) are ٥،۸۸ mA/cm^2, ۰،٦۲۳٥ V and ۰،۳۷۰٦ respectively.

Keywords: Dye-sensitized solar cells, Natural dye; Photoanode, Sol-gel method; TiO_2 nanoparticles

[Downloaded from www.opsi.ir on 2026-11-02]

١. Introduction

Dye-sensitized solar cells (DSSCs) have attracted considerable attention due to their low cost and easy fabrication with relatively high photo-conversion efficiency. O'Regan and Grätzel fabricated TiO_2 based DSSC for the first time in ١٩٩١ [١]. A typical DSSC is made up of semiconductor oxide film for attaching dye molecules, a counter electrode with deposited layer of platinum and an electrolyte solution. Sun light is absorbed by dye molecules and then electrons are injected to the conduction band of semiconductor oxide. Meanwhile oxidized dye molecules are regenerated by electrolyte solution also electrolyte ions regenerated through counter electrode. Semiconductor oxide film is the heart of DSSCs and the most studied materials are TiO_2, ZnO and SnO_2 which TiO_2 has announced as the best one due to its unique properties and various advantages such as photochemical stability, high band gap (~٣,٢ □□), □□□□ □□□□□□ □□□□□□□□ capability, availability, and non-toxicity. TiO_2 exists in three main phases, namely, rutile, anatase and brookite. However rutile phase is more thermal stable, anatase phase is the first choice for DSSCs applications due to its higher band gap energy [٢, ٣]. □□□□□□□□□ □□□□□□□ □□□ □□□□□□□ □□□ □□□□□□□□□ nanocrystalline TiO_2 such as sol-gel, hydrothermal, solvothermal and etc. which sol-gel is one of the most used methods due to highly crystalline and small size of synthesized nanoparticles [٤-٦]. The sol-gel is a simple, fast, and cost-effective method, which has received much attention due to providing controlled grain size as well as particle morphology, achieving superior purity, compositional homogeneity, low processing temperature, and production with simple equipment. In this work, natural dyes were used to reduce costs and TiO_2 nanoparticles were synthesized using sol-gel method. Then, DSSC was fabricated based on synthesized TiO_2 and photovoltaic performance was evaluated under AM ١,٥ G by measuring current-voltage curves and calculating η, V_{oc}, J_{sc}, and FF.

٢. Experimental

٢,١. Materials

The Titanium (IV) isopropoxide ($Ti[OCH(CH_3)_2]_4$), ethanol (C_2H_5OH), distilled water, nitric acid (HNO_3), polyethylene glycol ($C_{2n}H_{4n+2}O_{n+1}$), acetonitrile (C_2H_3N), potassium iodide (KIO_3) and iodine (I_2), ethylene glycol ($C_2H_6O_2$), platinum (Pt). Syzygium Cumini fruit and fluorine-doped tin oxide (FTO) conductive glass (sheet resistance ١٥Ω/sq).

٢,٢. Preparation of TiO_2 nanoparticles paste

In this method, TiO_2 nanoparticles were synthesized in anatase phase. First, titanium (IV) isopropoxide was added to ethanol under stirring and after few minutes, distilled water was added. Then adding few drops of nitric acid was done to control the pH of prepared solution. To form sol, solution must be stirred vigorously for ٣٠ min, then aging for ٢٤ hrs to obtain gel. For preparing TiO_2 nanoparticles from gel, it must be dried at ١٢٠ ºC then, sintered at ٤٥٠ ºC to get white powder [٤]. The procedure of TiO_2 synthesis is shown in Fig.١. Finally, TiO_2 powder and polyethylene glycol were mixed into the mortar until uniform paste was obtained [٧].

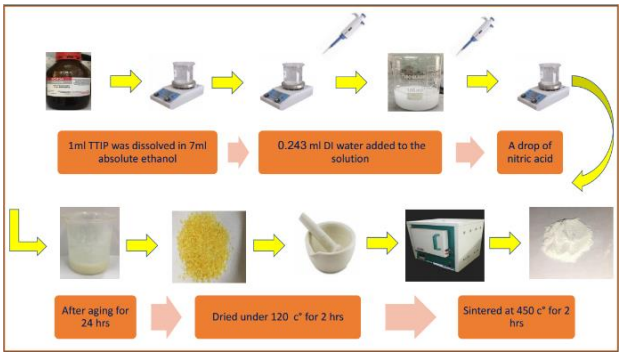


Fig. ١: The schematic of the synthesis route for TiO_2 via sol-gel method

٢,٣. Preparation of natural dye and electrolyte

It was extracted from fresh Syzygium Cumini fruit and ethanol was used as solvent [٨,١٠]. For preparation of electrolyte solution, first, ١٠ ml acetonitrile was added to ٢,٥ ml ethylene glycol under stirring. Subsequently, ١,٠٣٧٥ g potassium iodide and ٠,٣٣٠٧ g iodine was added

[Downloaded from www.opsi.ir on 2026-11-02]

respectively. Prepared electrolyte was stirred until homogenous solution appeared [۹].

۲,۴. Fabrication of DSSC

First, FTO glass substrate ultrasonically cleaned in deionized water, hydrochloric acid, acetone and ethanol respectively and dried at ۷۰ ºC. Afterwards, the prepared TiO_2 paste was coated on FTO glass, to make photoanode, by doctor blade method and after a few minutes it was heated at ۱۲۰ ºC then, calcinated at ٤٥۰ºC. After cooling, the photoanode was immersed in dye solution and kept in darkness for ۲٤ hrs. For the counter electrode, a thin layer of platinum was deposited on another FTO glass substrate. Finally, photoanode and counter electrode were combined together and sealed using surlyn sheet and electrolyte was injected between them. The active area of the electrode was ۰,۲٥ cm^2. The photograph of the fabricated DSSC is given in Fig.۲.




Fig. ۲: The fabricated DSSC

۳. Results and Discussion

Figure. ۳ shows the UV-vis absorption spectra in the range of ۳۰۰-۸۰۰ nm, which is shown a peak in ۳۸۰ □□.□□ □□□ □□□□ □□ □□□□□□□□□□ □□□□□□□□□□, □□□□□ become sharper and the absorbance increases. The FT-IR spectroscopy of the sample were studied which were synthesized via sol-gel method in the range of ٤۰۰–٤۰۰۰ cm^{-1}.and shown in Fig.٤. In this curve, peaks at ٤۲٥ cm^{-1} and ۷۳۲ cm^{-1} are for O–Ti–O bonding in anatase morphology. The bands centered at ۲۰٤۷ cm^{-1} and ۳۱۸۲ cm^{-1} are the characteristic of surface-adsorbed water and hydroxyl groups. Existing fine peaks also relate to the residual components of organic matter and reactions between water and carbon dioxide, while the last peak is attributed to the TiO_2. As well, XRD pattern was done to determine crystal structure of the prepared TiO_2 powder. The XRD peaks in the range of 2θ from ۲۰°-۹۰°, where the peaks in ۲٥,٤۱۸°, ۳۷,۲۰۸°, ۳۸,۱٤۳°, ٤۸,۲۲٦°, ٥٤,۳٤٤°, ٥٥,۲۹۲°, ٦۳,۰۸٥°, ۷۰,٥۸٦°, ۷٥,٥۷٥°, and ۸۳,۱۱٤° can be attributed to the ۱۰۱, ۱۰۳, ۱۱۲, ۲۰۰, ۱۰٥, ۲۱۱, ۲۰٤, ۲۲۰, ۲۱٥, and ۲۲٤ crystalline structures of anatase. This pattern is represented in Fig.٥.

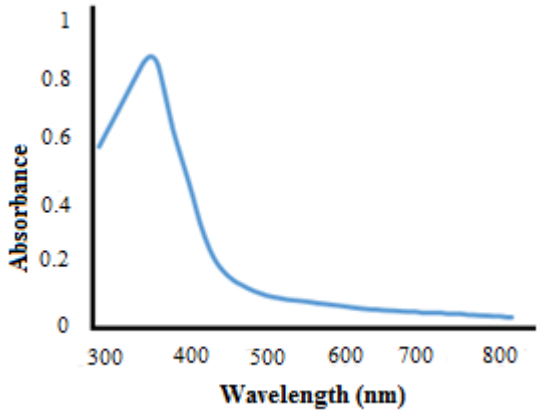


Fig. ۳: The UV-visible of the fabricated DSSC

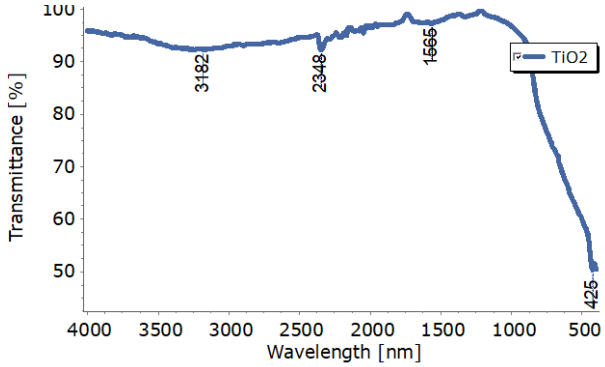


Fig. ٤: The FTIR of the fabricated TiO_2 nanoparticles

The current density–voltage (J–V) characteristics is represented in fig. ٦ and photovoltaic parameters of fabricated DSSC are calculated from this curve with incident light intensity of ۱۰۰ mW/cm^2 and AM ۱,٥. □□□ □□□□□□□□ □□□□□□□ □□□□□ □□□□□ □□□□□□□□□□□ efficiency of fabricated cell is ۱,۳٦٪ whereas calculated photovoltaic parameters such as short circuit current density (J_{SC}), open circuit voltage (V_{OC}) and fill factor (FF) are ٥,۸۸ mA/cm^2, ۰,٦۲۳٥ V and ۰,۳۷۰٦, respectively and with good agreement with pervious works [۸,۱۰]. The results approved the existence of free carriers by light

[Downloaded from www.opsi.ir on 2026-11-02]

photons absorption. It is expected to enhance the efficiency of dye adsorption by increasing the grain boundaries of the produced TiO_2 using sol-gel method.

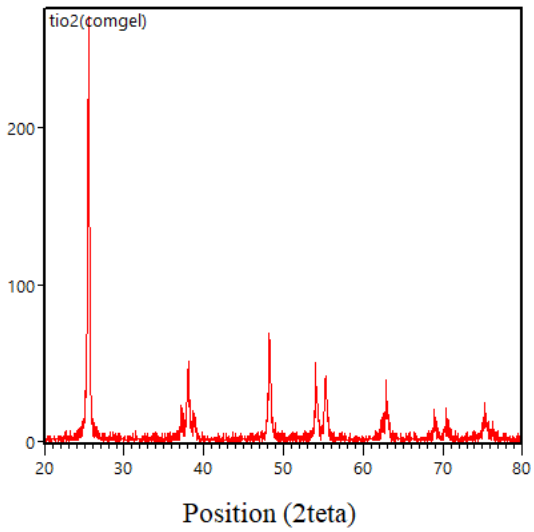


Fig. ٥: Powder XRD pattern of the TiO_2 nanoparticles

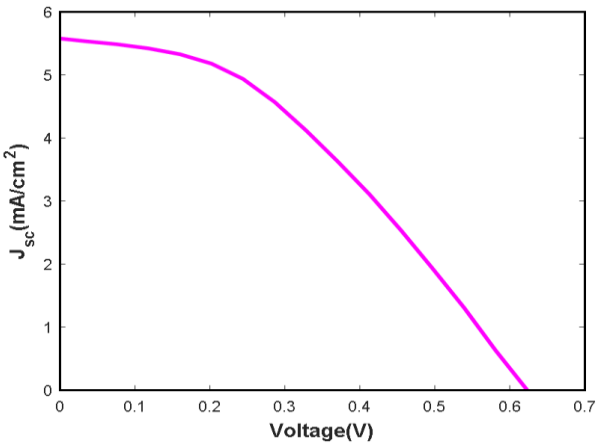


Fig. ٦: current density–voltage curve of the fabricated DSSC

۴. Conclusion

TiO_2 nanoparticles have been successfully synthesized using sol-gel method. The synthesized TiO_2 nanoparticles were characterized using XRD, and FTIR techniques. The produced nanoparticles were used as a part of photoanode in the DSSCs. The pastes were prepared with simple method and used in the photoanode of the fabricated DSSCs. The crystallography of the pastes, using X-ray illustrated the existence of TiO_2 in the anatase phase in all samples. The fabricated TiO_2-based DSSCs demonstrated a light to the electricity conversion efficiency of ۱,۱۳٪ with a fill factor of ۳۷,٥٪, open-circuit voltage of ۰,٦۲ V, and short-circuit current of ۳,۷ mA/cm^2.

References

[۱] O'Regan, B., & Grätzel, M. (۲۰۱۸). A Low-Cost, High-Efficiency Solar Cell Based on Dye-Sensitized Colloidal TiO_2 Films. In Renewable Energy (pp. ۲۰۸-۲۱۳). □□□□□□□□□□.

[۲] Sharma, A., Karn, R. K., & Pandiyan, S. K. (۲۰۱٤). Synthesis of TiO_2 nanoparticles by sol-gel method and their characterization. J Basic Appl Eng Res, ۱(۹), ۱-٥.

[۳] Li, G., Richter, C. P., Milot, R. L., Cai, L., Schmuttenmaer, C. A., Crabtree, R. H., ... & Batista, V. S. (۲۰۰۹). Synergistic effect between anatase and rutile TiO_2 nanoparticles in dye-sensitized solar cells. Dalton Transactions, (٤٥), ۱۰۰۷۸-۱۰۰۸٥.

[٤] Vijayalakshmi, R., & Rajendran, V. (۲۰۱۲). Synthesis and characterization of nano-TiO_2 via different methods. Archives of Applied Science Research, ٤(۲), ۱۱۸۳-۱۱۹۰.

[٥] Maurya, I. C., Senapati, S., Singh, S., Srivastava, P., Maiti, P., & Bahadur, L. (۲۰۱۸). Effect of Particle Size on the Performance of TiO_2 Based Dye-Sensitized Solar Cells. ChemistrySelect, ۳(۳٤), ۹۸۷۲-۹۸۸۰.

[٦] Jeng, M. J., Wung, Y. L., Chang, L. B., & Chow, L. (۲۰۱۳). Particle size effects of TiO_2 layers on the solar efficiency of dye-sensitized solar cells. International Journal of Photoenergy, ۲۰۱۳.

[۷] Kumar, K. A., Subalakshmi, K., & Senthilselvan, J. (۲۰۱٦). Effect of mixed valence state of titanium on reduced recombination for natural dye-sensitized solar cell applications. Journal of Solid State Electrochemistry, ۲۰(۷), ۱۹۲۱-۱۹۳۲.

[۸] Golshan, M., Osfouri, S., Azin, R., & Jalali, T. (۲۰۲۰). Fabrication of optimized eco-friendly dye-sensitized solar cells by extracting pigments from low-cost native wild plants. Journal of Photochemistry and Photobiology A: Chemistry, ۳۸۸, ۱۱۲۱۹۱.

[۹] Gu, P., Yang, D., Zhu, X., Sun, H., Wangyang, P., Li, J., & Tian, H. (۲۰۱۷). Influence of electrolyte proportion on the performance of dye-sensitized solar cells. AIP Advances, ۷(۱۰), ۱۰٥۲۱۹.

[Downloaded from www.opsi.ir on 2026-11-02]

[۱۰] Hambali, N. A. M. A., Yusof, N. R., Norhafiz Hashim, M., & Mat Isa, S. S. (۲۰۱٥). Dye-Sensitized Solar Cell Using Syzygium Cumini Fruit as Natural Dye Utilizing Titanium Dioxide. In Applied Mechanics and Materials ۷٥٤–۷٥٥, ۱۱۷۷.

[Downloaded from www.opsi.ir on 2026-11-02]